

ULRR

Investigation of electrode patterns suitable for nano-litre drop coated conducting polymer composite sensors

Item Type	Meetings and Proceedings
Authors	Arshak, Khalil;Cunniffe, Colm;Moore, Edward G.;Cavanagh, Leon M.
Citation	25th International Conference on Microelectronics;
Publisher	IEEE Computer Society
Download date	2026-03-05 23:53:48
Item License	https://creativecommons.org/licenses/by-nc-sa/1.0/
Link to Item	https://hdl.handle.net/10344/1162

Investigation of Electrode Patterns Suitable for Nano-Litre Drop Coated Conducting Polymer Composite Sensors

K.I. Arshak, C. Cunniffe, E.G. Moore and L.M. Cavanagh

Abstract— This study presents an analysis of electrode patterns suitable for use with drop coated conducting polymer gas sensors. A thin-film technique was used to efficiently fabricate the copper electrode patterns [1]. Conducting Polymer Composite (CPC) materials were deposited using a 500 nano-litre syringe onto the electrode patterns to produce an array of sensors for organic solvent vapour detection. The sensors were exposed to propanol vapour in steps of 3000 ppm from a minimum concentration of 5000 ppm up to a maximum concentration of 20,000 ppm. Empirical results showed that a non-parallel electrode configuration produces a marginally larger response and is also less noisy than the interdigitated or parallel electrode configurations. Results show that increasing the baseline resistance of the sensing material gives a larger response.

I. INTRODUCTION

Much research has been carried out in the area of electrode geometry for use in gas sensors in the past [2], [3]. Previous works investigated the effect of geometry and position of electrodes for semi-conductor gas sensors [3]. It was discussed in the conclusion that placing electrodes beneath the sensing layer is not the optimal site, but if they are placed as such a wider electrode gap increases sensitivity [3]. It was also observed in a recent work [4] that noise levels decrease as electrode gap distances increase with electrode gaps ranging from $20\mu\text{m}$ - $140\mu\text{m}$ where it was stated that the underlying physics causing this was still being investigated. Previous work on electrode patterns for use with polymer carbon-black composites was carried out where spray coating was used to deposit the sensing material resulting in a homogenous sensing layer [2]. The electrode patterns investigated included 42 circular configurations. It was shown in that work that the electrode geometry did not have an effect on sensor response magnitude but noise properties are strongly effected by electrode configuration [2]. It is the aim of this work to investigate the optimal electrode pattern for use beneath a drop coated conducting polymer composite sensing material. The material was deposited using a drop coating technique. Upon deposition of the

material drop the conducting polymer composite dispersed to form a ring structure. A number of different patterns (Fig. 2) were investigated to show which patterns yield noisy responses. Different gap widths in parallel electrode configuration were tested to find a relationship between gap width and baseline resistance. A range of sensor baseline resistances were also used to find correlations between baseline resistance and sensor response. The sensor arrays were exposed to solvent concentrations of 5000ppm to 20000ppm in increments of 3000ppm.

II. EXPERIMENTAL

The sensors were produced on an alumina substrate, which was coated with a layer of copper using an Edwards Thermal Evaporation unit. The resulting substrate was then coated with photo resist using a spin coater. Patterns were designed using Eagle PCB software and printed on acetate. The pattern was UV exposed onto the substrate, and then subsequently dipped in developer and etched. The remaining photoresist was then striped from the pattern on the substrate. A more detailed description of this process is described in [1]. The sensing material composed of carbon black, polyethylene adipate, and surfactant as described earlier [5] and drop coated using a 500 nano litre syringe set to deposit 100 nano litres. The drop coating apparatus is shown in Fig. 1

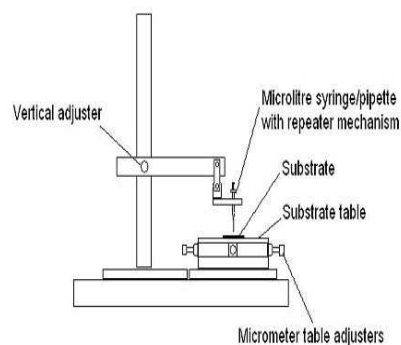


Fig. 1. Setup Used For Drop Coating Sensor Materials.

K.I. Arshak, C. Cunniffe, E.G. Moore and L.M. Cavanagh are with the Microelectronic and Semiconductor Research Group, Department of Electronic and Computer Engineering, University of Limerick, National Technological Park, Limerick, Ireland. Email: khalil.arshak@ul.ie

The 25.4mm x 12.7mm alumina substrate may be inserted into the testing equipment to enable the patterns to the left of the substrate (Fig. 2) to be tested and then inserted to allow the patterns on the right of the substrate (Fig. 2) to be tested. The sensor arrays were placed in a dynamic flow gas test chamber, which permitted the arrays to be exposed to specific vapour concentrations in a controlled manner. The chamber used a Bronkhorst EL-Flow mass flow meter/controller to control the carrier gas and a μ -Flow liquid mass flow meter with a Controlled Evaporator Mixer (CEM). An EZ-7000 controller unit was used to manually operate the liquid and gas flow controllers. The system was serially connected to a PC for automatic operation. The sensors were exposed to propanol vapour in steps of 3000 ppm from a minimum concentration of 5000 ppm up to a maximum concentration of 20,000 ppm. The exposure cycle consisted of a 30 seconds flush period followed by 60 seconds exposure to the solvent vapour and another 30 seconds flush. The array responses were recorded using a National Instruments data acquisition card (Model No: PCI-MIO-16E-4) and LabVIEW software.

III. RESULTS AND DISCUSSION

Electrode patterns (Fig. 2) were drafted using Cadsoft Eagle PCB design software such that two different configurations may be tested using one drop of sensing material to eliminate sensor-to-sensor reproducibility issues. This allowed for direct comparisons between electrode configurations for each drop of sensing material deposited across each electrode. The electrode configurations consisted of varying gaps between the points and different angles of attack of electrode into the drop of sensing material as well as an interdigitated configuration (Fig. 2). Table I details the electrode gaps at each stage of the manufacturing process and Table II details the baseline resistance of the sensors.

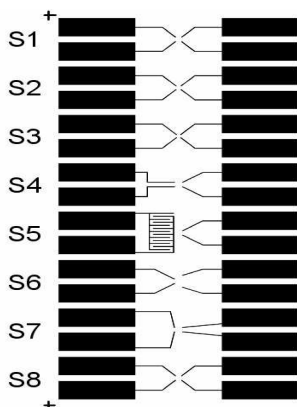


Fig. 2. Electrode pattern allowing for the testing of two electrode patterns.

TABLE I
ELECTRODE GAPS SPECIFICATION (ALL FIGURES IN μM)

Sensor	Process Stage	Left	Right
S1	CAD Output	200	200
	Mask	97.9	116.6
	Etched Pattern	102.6	166.6
S2	CAD Output	150	150
	Mask	0	0
	Etched Pattern	0	0
S3	CAD Output	100	100
	Mask	0	0
	Etched Pattern	0	0
S4	CAD Output	200	200
	Mask	121.2	116.6
	Etched Pattern	107.2	135.2
S5	CAD Output	200	200
	Mask	\sim 107	111.9
	Etched Pattern	\sim 121	121.2
S6	CAD Output	200	700
	Mask	135.3	587.4
	Etched Pattern	139.9	596.7
S7	CAD Output	200	200
	Mask	172.6	103.4
	Etched Pattern	158.5	111.9
S8	CAD Output	200	200
	Mask	103	107.3
	Etched Pattern	93.24	95

These configurations presented a method of determining the important features of the dropped sensing material. A stereomicroscope image of the acetate mask focused on S4 is presented in Fig. 3, and the etched pattern of S4 is displayed in Fig. 4.

A volume of 100 nano-litres of Polyethylene adipate\carbon black composite material was deposited onto the electrodes using a nano-litre drop coating technique. Fig. 5 shows a stereomicroscope image of the resulting sensor with the deposited material focusing on S4. The image shows the electrodes beneath the material in both a parallel and non parallel configuration. The ring structure which is formed on deposition and is the most significant constituent element of the material is also visible in Fig. 5.

By varying the structure of the electrode patterns the resultant data showed that the most important structure of the sensing material is the ring structure around the edge of the dropped material. The electrode gap in the middle of the sensing material had little effect whereas the distance between the electrodes where the ring crossed over the electrode defined the baseline resistance of the sensor. Sensors with a higher baseline resistance boasted a larger and less noisy response while the sensors with electrodes, which lay parallel to each other,

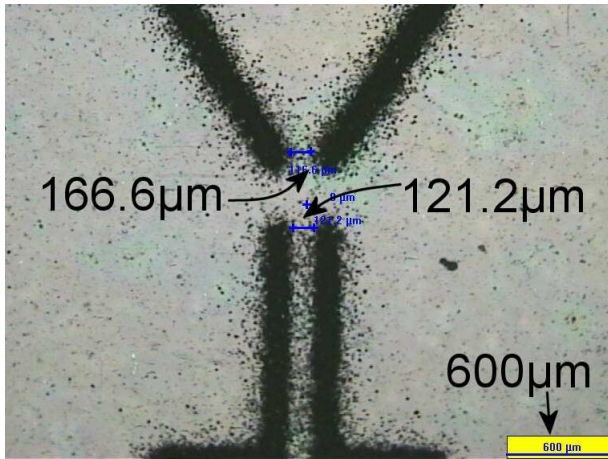


Fig. 3. Stereomicroscope image focusing on S4 of mask printed on acetate.

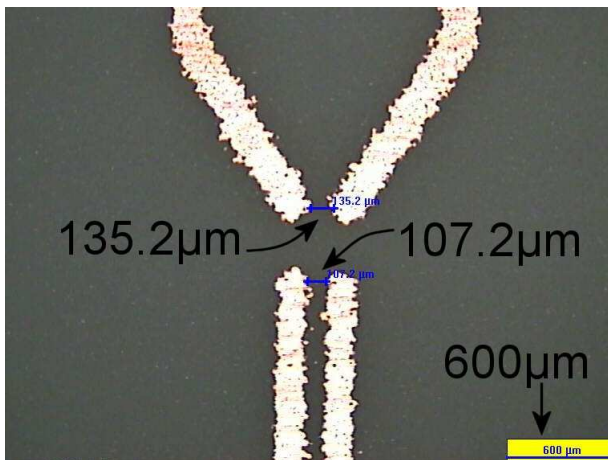


Fig. 4. Stereomicroscope image focusing on S4 of etched pattern.

produced noisy response such as the patterns S4 and S5 in Fig. 2. The sensor responses were pre-processed using fractional baseline manipulation, shown in Equation. (1) which produces a normalised response and can enhance contrast and reduce drift effects [6].

$$V = \frac{V_{gas} - V_{air}}{V_{air}} \quad (1)$$

Where V_{gas} is the voltage drop across the sensor in response to the vapourised solvent and V_{air} is the voltage drop across the sensor in response to the flush gas.

A typical response for sensor pattern S4 is displayed in Fig. 6 showing that the parallel electrodes produces a noisy response and the alternative pattern on the right hand side of S4 yielded a cleaner response and also exhibited a marginally larger response. Fig. 7 shows a typical response from an interdigitated electrode pattern.

To test the effect of electrode gap width in a parallel configuration an array was designed with increasing gap sizes from $200\mu\text{m}$ to $800\mu\text{m}$. The maximum $\Delta V/V\%$

TABLE II
BASELINE RESISTANCES OF SENSORS (ALL FIGURES IN $k\Omega$)

Sensor	Baseline Resistance	
	Left	Right
S1	145.5	186.5
S2	0	0
S3	0	0
S4	29	34.75
S5	20	138
S6	48.2	64
S7	75.5	31.56
S8	69.45	59.3

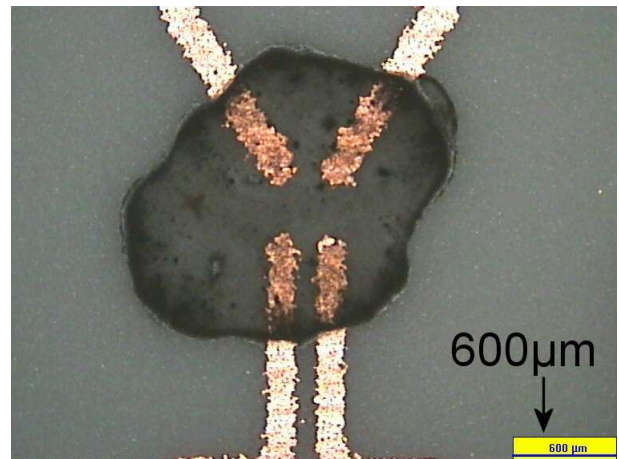


Fig. 5. Stereomicroscope image focusing on S4 of etched pattern with deposited material showing ring structure.

was extracted from the raw data. Fig. 8 shows the resulting graph of baseline resistance versus percentage change of voltage the seven parallel electrode configurations with varying gaps. The $\Delta V/V\%$ vs R_0 graph shows a trend in the data illustrating that the percentage voltage change increases as the baseline resistance increases, however the electrode Gap vs R_0 graph also shows there was no correlation between the baseline resistance of the sensor and the electrode gap width. Employing interdigitated electrodes for this applications didn't enhance the sensor response. Due to the parallel nature of the interdigitated fingers the sensor exhibited a similar but more exaggerated noisy response illustrated in Fig. 7 to that of the parallel electrodes. The interdigitated configuration contribute to lowering the baseline resistance but as shown in Fig. 8 a higher baseline resistance yields a better percentage voltage change.

IV. CONCLUSION

Results show that increasing the baseline resistance of the sensing material gives a larger response and there is

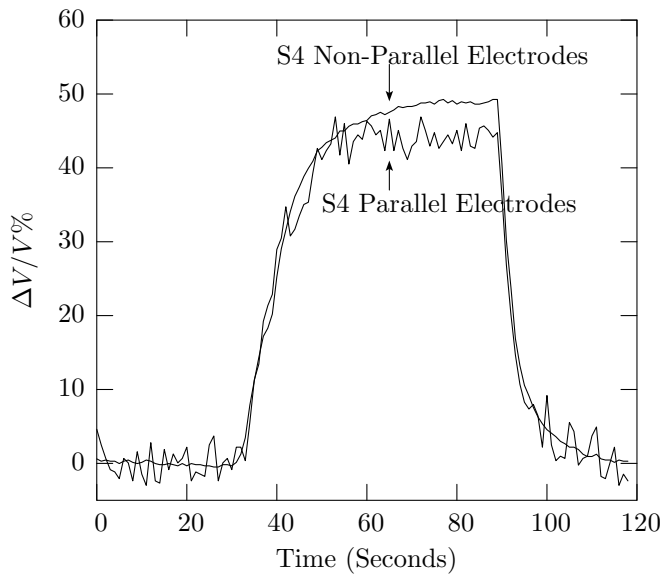


Fig. 6. Graph showing the typical response of PEA sensors response to 20000ppm of Propanol using electrode pattern S4.

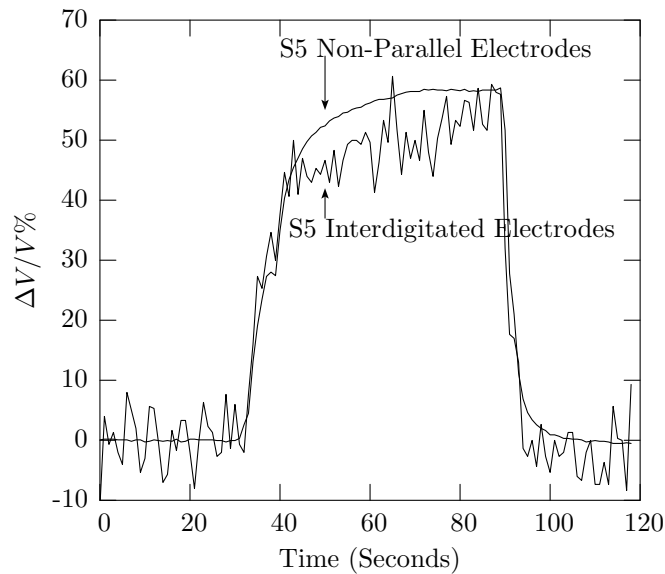


Fig. 7. Graph showing the typical response of PEA sensors response to 20000ppm of Propanol using electrode pattern S5.

no correlation between the baseline resistance and the electrode gap in a parallel configuration. Empirical results showed that a non-parallel electrode configuration produces a marginally larger response and is also less noisy than the interdigitated or parallel electrode configurations. The electrode gaps are less important due to the material deposition method as the principle components of the material disperse to the edges to form a ring structure which governs the base line resistance. This work shows that manipulating the electrode pattern can improve the sensitivity and stability of these drop coated conducting polymer composite sensors for use in electronic nose applications.

ACKNOWLEDGEMENTS

This work was conducted as part of a collaborative project between AMT Ireland, University of Limerick and University College Cork, and is funded by Enterprise Ireland under project ref. no. ATRP/2002/427 (Intelli-SceNT).

REFERENCES

- [1] K. Arshak, C. Cunniffe, E. Moore, L. Cavanagh, and J. Harris, "A novel approach to electronic nose-head design, using a copper thin film electrode patterning technique," in *28th International Spring Seminar on Electronics Technology*, Austria, 2005, pp. 185–190.
- [2] B. Matthews, J. Li, S. Sunshine, L. Lerner, and J. Judy, "Effects of electrode configuration on polymer carbon-black composite chemical vapor sensor performance," *Sensors Journal, IEEE*, vol. 2, no. 3, pp. 160–168, 2002.
- [3] X. Vilanova, E. Llobet, J. Brezmes, J. Calderer, and X. Correig, "Numerical simulation of the electrode geometry and position effects on semiconductor gas sensor response," *Sensors and Actuators B: Chemical*, vol. 48, no. 1-3, pp. 425–431, May 1998.
- [4] V. T. Wong, A. Huang, and C.-M. Ho, "Towards high density silicone polymeric chemical vapor sensor arrays," in *Proceedings of 11th International Symposium on Olfaction and Electronic Nose (ISOEN'05)*, vol. -, no. -, Barcelona, Spain, Apr. 2005, pp. 398 – 401.
- [5] K. Arshak, E. Moore, L. Cavanagh, J. Harris, B. McConigly, C. Cunniffe, G. Lyons, and S. Clifford, "Determination of the electrical behaviour of surfactant treated polymer/carbon black composite gas sensors," *Composites Part A: Applied Science and Manufacturing*, vol. 36, no. 4, pp. 487–491, 2005.
- [6] R. Gutierrez-Osuna, "Pattern analysis for machine olfaction: a review," *Sensors Journal, IEEE*, vol. 2, no. 3, pp. 189–202, 2002.

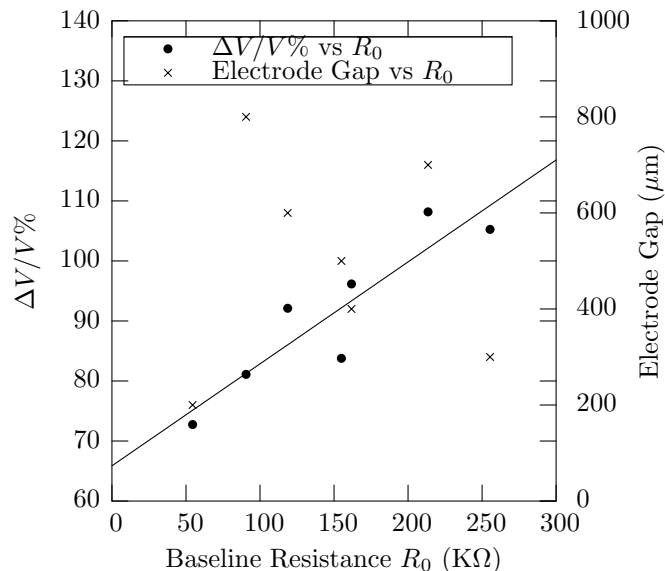


Fig. 8. Plot of Baseline Resistance vs Change in Voltage and Electrode Gap for Seven Parallel Plate Electrodes